

Evaluation and utilization of polymeric plastic wastes in concrete blocks

Darweesh HHM

ABSTRACT

There is however a dearth in the utilization of plastic pellets made of polyvinyl chloride (PVC) and polystyrene (PS) in concrete blocks. Hence, the current research investigated the exploitation of PVC and PS pellets in the production of concrete blocks. So, the PVC and PS were used as fine aggregates in concrete blocks. Two concrete block mixtures were prepared to evaluate their workability, bulk density, apparent porosity and compressive strength. The prepared samples of concrete mixture was substituted by 0, 5, 10, 15, 20 and 25 % of either PVC or PS. Results illustrated that PS absorbs more water than that of PS which absorbs less water. The workability of both PVC and PS concrete blocks improved and enhanced as the content of PVC and PS plastic wastes was increased. The compressive strengths of the PS concrete blocks were slightly higher than those of PVC at any content. This implied that the incorporation of PS plastic wastes can be a propitious solution to the plastic waste dilemma and demand for stronger concrete blocks.

Keywords: Cement, plastic wastes, blocks, density, porosity, strength.

To Cite:

Darweesh HHM. Evaluation and utilization of polymeric plastic wastes in concrete blocks. *Indian Journal of Engineering*, 2021, 18(50), 258-266

Author Affiliation:

Refractories, Ceramics and Building Materials
Department, National Research Centre, Cairo, Egypt
Email : hassandarweesh2000@yahoo.com

Peer-Review History

Received: 29 May 2021

Reviewed & Revised: 31/May/2021 to 02/July/2021

Accepted: 03 July 2021

Published: July 2021

Peer-Review Model

External peer-review was done through double-blind method.

1. INTRODUCTION

1.1. Scope of the problem

Population concurrently grows exponentially with the demand for food and infrastructure associated with plastic waste mismanagement and concrete consumption. However, there is a dearth in the utilization of plastic pellets using polyvinyl chloride (PVC) and polystyrene (PS) in concrete blocks. It is worth to mention that the growing of the exponential population has been produced ripple effects over thru decades. The preoccupation of this growth entails a growing number of problems in the demand and consumption of the fundamental needs of human beings, but not to mention the foods and the shelter, beside others. However, the processes underlying food production and materials for infrastructure as well as their preservation greatly contributed to a multifold and alarming increase in waste products.

Human beings always have been utilizing plastic materials in manufacturing, storing, and preserving foods. This seemed to be of a great catalyst to achieve such convenience. The benefits brought by the use of these plastics are stifled by its alarming effects on the environment. One of which is the staggering report on plastic debris in the ocean which has been recorded to



be 5.25 T pieces already with a rate of 8 million trashes from 192 coastal countries [1-3]. The coastal countries are intensely contributed to plastic pollution globally. Some countries discarded about 125 000 plastic bags of daily which did not surprise science specialists who were aggregating to 1.88 million tons of plastic wastes yearly. The recent battle with plastic mismanagement urged various organizations and local government units to set several politics to put an end to this environmental problem. Some of them act through implementing politics in partnership with different companies and organizations [3-6].

A side from food, the exponential demand for shelter and infrastructure entails the rise in the demand for construction materials with sufficient fresh and strength parameters to withstand any topographical and environmental risks and disasters such as typhoons and earthquakes. Water as first and followed by concrete hollow blocks (CHB) are the top two most consumed substances on Earth. These materials are of a big demand in the sector of industry for infrastructural projects [5-7].

Innovations have been established by replacing the aggregates of different materials to improve the parameters of concrete hollow blocks as compressive strength, workability, mechanical properties and others. Generally, fresh and strength parameters of concrete increase almost linearly as the percentage of replacement increases. The studies have established the fact that replacing the constituents of concrete affects the fresh and strength parameters of concrete [1, 8-20].

Replacing fine aggregates with plastic waste materials abound in the scientific society to solve both the need for stronger concrete hollow blocks and solutions for recycling plastic wastes. The addition of fine aggregates to polypropylene pellets (PP) at the expense of fine aggregates is the main target of that study. However, there is a dearth of studies that maximize the use of other types of plastic materials like low-density polyethylene (LDPE), high-density polyethylene (HDPE), polyvinyl chloride (PVC), and polystyrene (PS) [14]. As the recommendation of the latter study, extensive investigation on the use of different types of plastic wastes aside from PP and measurement of other strength parameters should be further conducted. The present study characterized PVC and PS pellets as concrete hollow blocks reinforcement; determined the effects of varying percentage replacement of fine aggregate with PVC and PS pellets on the fresh and strength parameters of concrete hollow blocks such as workability and compressive strength; and compared the PVC- and PS-blended concrete hollow blocks fresh and strength parameters.

1.2. Objectives of the study

The essential goal of the present investigation is to study and evaluate the influence of the dry plastic wastes of PVC and PS on the physical and mechanical properties of the prepared concrete block samples containing it in terms of workability, density, porosity and compressive strength.

2. EXPERIMENTAL

2.1. Raw materials

Plastic wastes that were manufactured by polyvinyl chloride (PVC) and/or polystyrene (PS) were provided by a local plant, Egypt. These waste materials were fine ground, processed and prepared before mixing. The Ordinary Portland cement (OPC Type I- CEM I 42,5R) having the blaine surface area or fineness 3400 cm²/g) as received was provided by a local supplier (El-Amrya cement factory, Alexandria, Egypt. At first, the pellets of PVC and PS were characterized before mixing as recommended in the cited literature [14]. The tap water is commonly used for mixing and curing with specific gravity of 1.00. The PVC sample is thermoplastic pellets that often used to make wire cable insulation were taken from a local plant that usually receives these ground residual wastes from several electronic companies. On the other side, PS sample was in the form of plastic cutlery wastes from the same plant. These cutleries were ground in a suitable grinding machine to achieve fine pellet size (Figure 1). These pellets were subjected to sieve analysis. Larger size of these pellets (> 4.75 mm) must be excluded because it may affect the strength of the tested samples [14]. These materials were characterized in terms of density and specific gravity using principles of Archimedes [14], bulk density [21], and absorption for 24 hours [22]. The used fluid in the characterization of PVC pellets was distilled water, while isopropyl alcohol was used for PS pellets due to the difference in specific gravity as shown in Table 1. The chemical analysis of the OPC as measured by X-ray florescence technique (XRF) is listed in Table 1, while its mineralogical constituent as calculated from Bogue equations is given in Table 2. The sand sample was brought from the desert of 6 October city, Giza, Egypt.



(A) Polyvinyl chloride (PVC) (B) Polystyrene (PS)

Figure 1: Pellets of Polyvinyl chloride (A) and polystyrene samples (B).

Table 1 - Chemical analysis of the OPC, Gbfs and PC raw materials, mass %.

Oxide Material	SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	CaO	MgO	MnO	SO ₃	Na ₂ O	Ti ₂ O	K ₂ O	LOI
OPC	20.12	4.25	1.29	63.13	1.53	0.36	2.54	0.55	0.19	0.30	2.64

Table 2 - Mineralogical composition of the OPC and Gbfs

Phase Materials	C ₃ S	C ₂ S	C ₃ A	C ₄ AF
OPC	65.78	8.67	8.24	11.71

2.2. Preparation and methods

The concrete mixture was prepared from OPC, sand and aggregates. The plastic wastes of PVC and/or PS pellets were substituted at the expense of sand. So, The mixtures of the first group were containing PVC, whereas the second group was incorporated PS. The first was composed of concrete mixture and PVC as 100:0, 96:5, 90:10, 85:15, 80:20 and 75:25 having the symbols: V0, V1, V2, V3, V4 and V5, respectively. The second was composed of concrete mixture and PS as 100:0, 95:5, 90:10, 85:15, 80:20 and 75:25 having the symbols T0, T1, T2, T3, T4 and T5, respectively. The composition of the concrete blends of the first group is illustrated in Table 3, whereas that of the second group is shown in Table 4, respectively.

Table 3- Mix composition of the first group composed of Concrete mixture and PVC (PC).

	Group I (PC)					
Mix Materials	V0	V1	V2	V3	V4	V5
Conc. Mix	100	95	90	85	80	75
PVC	0	5	10	15	20	25

Table 4-Mix composition of the second group composed from concrete mixture and PS (PS).

	Group II (PC)					
Mix Materials	T0	T1	T2	T3	T4	T5
Conc. Mix	100	95	90	85	80	75
PS	0	5	10	15	20	25

The blending process of the various cement batches was firstly done in a porcelain ball mill using three balls for two hours to assure the complete homogeneity of all cement batches. The materials of cement and sand were mixed in the ratio of 1:3, while water to cement mix was 0.5 by volume. During mixing, the suggested water ratio was poured on the cement powder in the mixer gradually. Then, the mixer was operated for 5 minutes with a mean velocity of 10 rpm to reach the entire matching pastes. Before casting, the moulds were covered by a thin layer of oil to easily the removal of cement cubes from the moulds on de-moulding

process. The prepared cement pastes were then moulded into stainless steel moulds of dimensions 4 x 8 x16 inches, and then vibrated manually for three minutes, and then on a mechanical vibrator for another three minutes to remove all air bubbles trapped inside the cement pastes. The moulds were completely casted with cement pastes and its surface was flattened with a suitable spatula [23-28]. After casting of samples, they were covered with a wet sheet during the first 24 hours to prevent moisture loss. The moulds were then placed in a humidity chamber for 24 hours under 95 ± 1 relative humidity (RH), and room temperature (23 ± 1), demoulded in the next day. After complete drying, the samples of concrete blocks were subjected to bulk density, apparent porosity, and compressive strength.

The workability of concrete mixtures was carried out through slump test [29]. It determines the conformity of fresh concrete before it hardens. It is performed to attain the workability of fresh concrete, and therefore, the ease with which concrete flows. Also, it can be used as an indicator of an improperly mixed batch. The bulk density (BD) and apparent porosity (AP) of the hardened concrete blocks [25-30] were calculated from the following equations:

$$\text{B.D. (g/cm}^3\text{)} = \frac{W1}{(W1-W2)} \times 1 \quad (1)$$

$$\text{A.P. \%} = \frac{(W1 - W3)}{(W1-W2)} \times 100 \quad (2)$$

Where, W1, W2 and W3 are the saturated, suspended and dry weights, respectively. The compressive strength (CS) of the various hardened concrete blocks [31,32] was measured and calculated from the following relation:

$$\text{CS} = \frac{L \text{ (KN)}}{S_a \text{ (cm}^2\text{)}} \times 102 \text{ (Kg/cm}^2\text{)}/10.2 \text{ (MPa)} \quad (3)$$

Where, L is the load taken, Sa is the surface area.

3. RESULTS AND DISCUSSIONS

3.1. Physical characteristics of PVC and PS

Plastic wastes were compared in terms of their physical properties as specific gravity, bulk density (g/cm^3), rate of absorption (%) and its behaviour in water. Table 5 and Figure 2 demonstrated the comparison between these waste raw materials. These values were used in mixing of the constituents of concrete blocks and are the basis for the justifications in the workability and compressive strength. As it is illustrated, the sand and PVC fine aggregates were sinking in the water, while PS fine aggregates were floating. Furthermore, the PVC has greater absorption ability than PS, i.e. for normal hydration, the concrete mixtures containing PS fine aggregates need water more than that of PVC fine aggregates [33-35]. Meanwhile, the PVC waste pellets sank in water. This in turn justified that whether the waste plastic pellet sinks or floats in water, it can be used as fine aggregate substitution for concrete structures [36,37].

Table 5- Physical properties of the used sand and plastic waste materials

Property Materials	Specific gravity	Bulk density, g/cm^3	Absorption, %	Behaviour in water
Sand	2.47	2.47	1.34	Sink
PVC	1.39	1.411	0.931	Sink
PS	1.03	0.973	0.103	Float

3.2. Workability

The workability of the various blended concrete structures as measured through slump test (mm) is shown in Figure 3. As it is clear, the workability increased as the amount of either PVC or PS plastic wastes increased in the concrete mixture. Moreover, the values of workability that obtained with PS are higher than those obtained with PVC. This principally attributed to the fact that the PS waste pellets required more water to produce suitable workability than that needed by PVC [14,33-35]. Accordingly, the workability of the blank recorded the lowest workability, while those containing 25 % of the two types of the plastic wastes achieved the highest [14,17,31,36,37]. However, the cement structures incorporating PS exhibited slump values higher than those containing PVC at all replaced quantities.

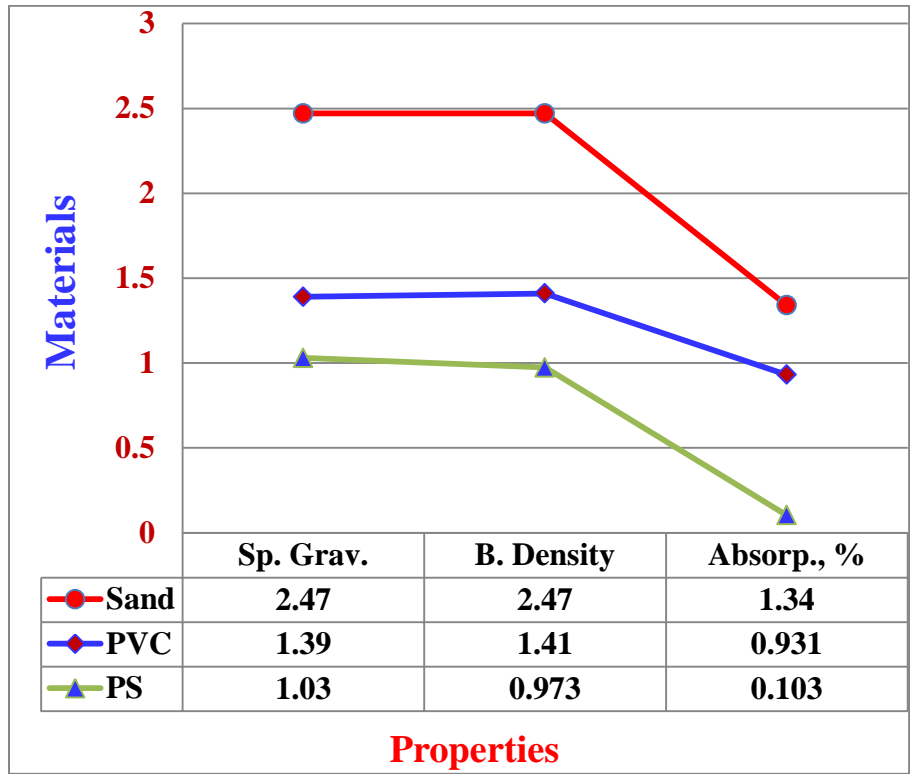


Figure 2- Physical properties of the used sand and plastic waste materials.

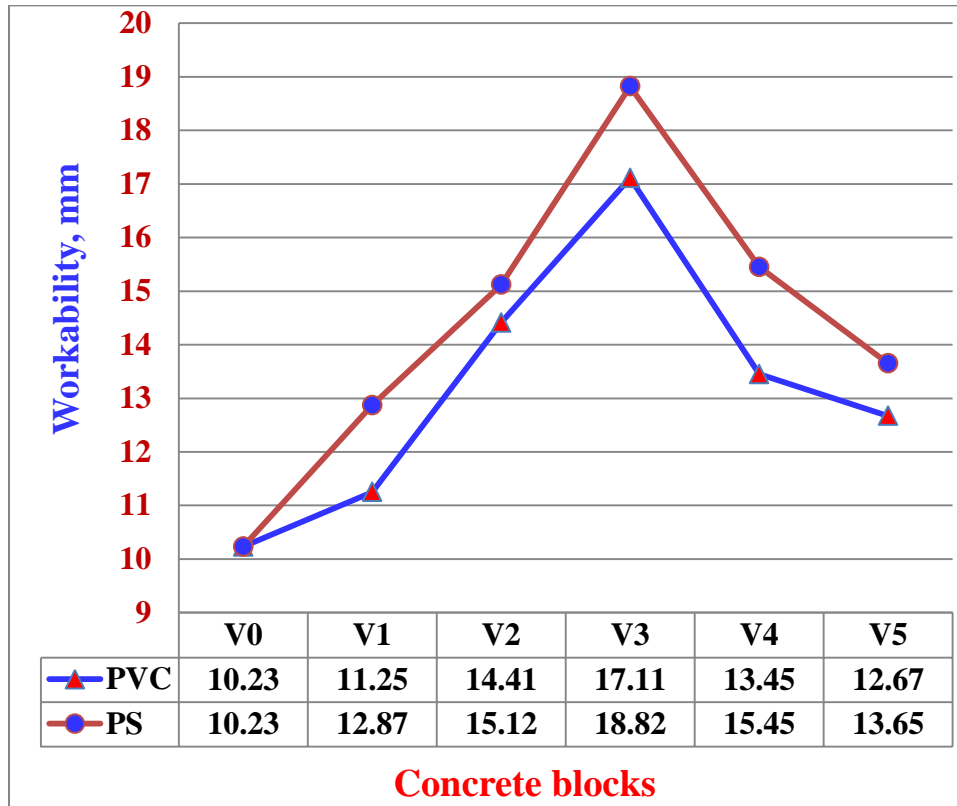


Figure 3-Workability of the various concrete structures with or without PVC and PS plastic wastes.

3.3. Bulk density and apparent porosity

The bulk density and the apparent porosity of the various blended concrete structures are represented as a function of concrete blocks in Figures 4 and 5, respectively. As it is shown, the apparent porosity of the concrete block samples decreased as the content

of both PVC and PS increased, while the bulk density increased. This could be taken place only up to 25 %, of the two types of plastic wastes (V3 and T3). With further increase of PVC or PS contents, the apparent porosity started to increase, while the bulk density diminished (V4, V5 and T4, T5). Moreover, the apparent porosity of concrete blocks containing PS is lower than those containing PVC plastic wastes whereas the bulk density is higher. This occurred with all quantities of either PS or PVC. This may be due to the greater rate of absorption of PS than PVC plastic wastes, which allowed to improve and enhance the rate of hydration [13,17,20,37]. So, these concrete mixtures can be utilized in many massive structures like dams, bridge piers and even canals [38,39].

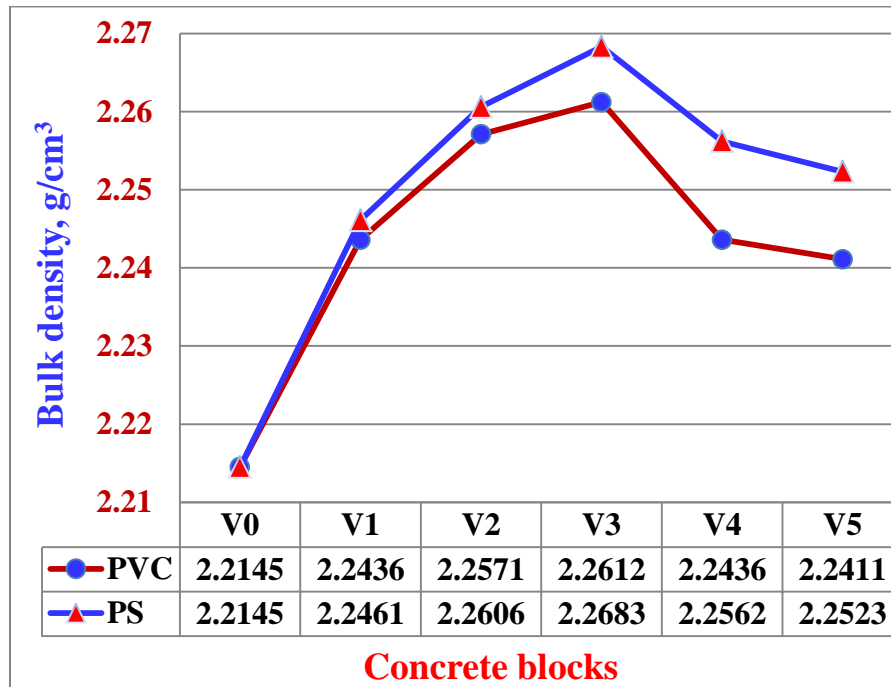


Figure 4-Bulk density of concrete blocks with and without PVC and PS plastic wastes

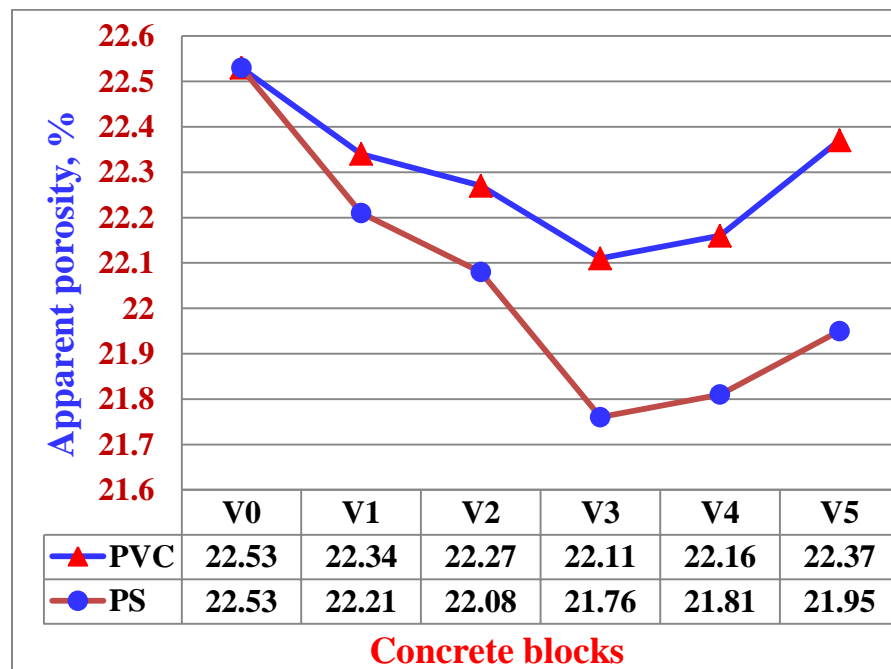


Figure 5-Apparent porosity of concrete blocks with and without PVC and PS plastic wastes.

3.4. Compressive strength

The results of compressive strength of the various blended concrete blocks are graphically plotted as a function of concrete blocks in Figure 6. The compressive strength of the blank is 4.14 MPa. This value was slightly increased with the blending the concrete

mixture with both PVC or PS plastic wastes, but only up to 25 % of either PVC or PS (V3 and T3), and then declined with further increase of either. Furthermore, the compressive strength of concrete mixtures incorporating PS is slightly higher than those containing PVC. Also, the compressive strength of both groups achieved the same trend, i.e. behaved like others. The increase of compressive strength is essentially contributed to that the PS waste pellets diminish the porosity of the tested samples more than in case of PVC, in addition that the PS improved the hydration of concrete mixture more than that of PVC [13,14,23,24]. Meanwhile, Batch T3 containing 25 % PS plastic pellets and Batch V3 incorporating 25% PVC plastic pellets attained the highest values of compressive strength as the experimental data demonstrated. These data and notifications were confirmed in several studies [13,17,20,39-41]. This trend was attributed to the lower absorption of the pellets in general resulting in a greater amount of water suitable for the hydration of the concrete mixture. However, the concrete blocks with PS plastic pellets are better than those with PVC.

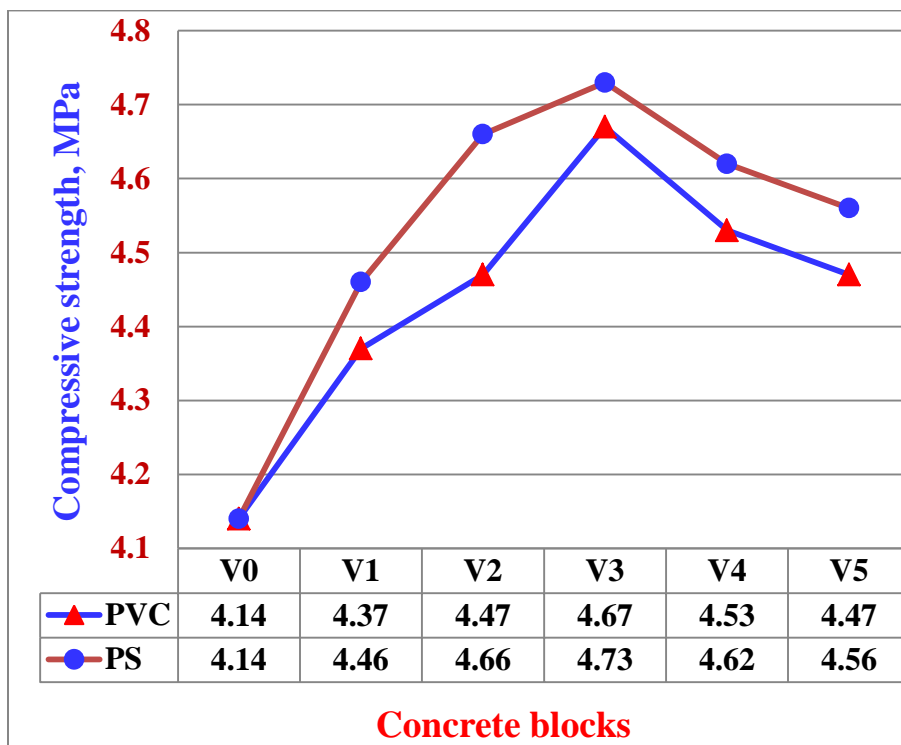


Figure 6 - Compressive strength of concrete blocks with and without PVC and PS plastic wastes.

4. CONCLUSIONS

The following overall conclusions could be obtained:-

1. Due to density and specific gravity properties, the PVC plastic waste pellets are floating when placed in water, while PS plastic waste pellets are sinking. Also, the PVC plastic waste pellets have greater absorption ability than PS plastic waste pellets, where both were lower than those of the used sand. The PVC plastic waste pellets absorb water more than PS plastic pellets, i.e. if the pellets are mixed in two different concrete mixtures, there will be more water available in the PS mixture than in the PVC mixture for hydration.
2. The workability due to slump test of fresh concrete mixtures increased as the content of both PVC and PS plastic waste pellets increased. The slump values of the prepared concrete blocks from both PVC and PS plastic waste pellets are seemed to be suitable for roads and some massive concrete blocks for dams, bridge and canal locks or piers.
3. The compressive strength of the prepared concrete blocks enhanced with the increase of PVC or PS plastic waste contents, only up to 25 %, but then decreased with further increase of it. Furthermore, the compressive strength of concrete blocks incorporating PS plastic wastes was higher than those containing PVC plastic waste pellets at any amount. It is good mention that this is a propitious solution to solve problems of plastic waste management of PS type of plastic and the demand for stronger concrete blocks in the infrastructure industry.

- Further investigations must be done to identify whether greater quantities from PVC or PS plastic wastes more than 25 % can be considered. In addition, other forms and grain sizes as fibres or flakes of these plastic waste pellets or any other plastic wastes can be exploited.

Acknowledgement

The author wishes to express his deep thanks for National Research Centre for helping to obtain materials, processing, preparing, molding and measuring all of the obtained data of this study, and moreover for financial assistance.

Funding

This study has not received any external funding.

Conflict of Interest

The author declares that there are no conflicts of interests.

Data and materials availability

All data associated with this study are present in the paper.

REFERENCES AND NOTES

- Sharma R; Bansal PP (2015) Use of Different Forms of Waste Plastic in Concrete – A Review. *Journal of Cleaner Production*. <https://doi.org/10.1016/j.jclepro.2015.08.042>
- Parker L (2015) Ocean Trash: 5 25 Trillion Pieces and Counting , but Big Questions Remain. *National Geographic*. <https://www.nationalgeographic.com/news/2015/1/150109-oceans-plastic-sea-trash-science-marine-debris/>
- Dunham W (2015) World's Oceans Clogged by Millions of Tons of Plastic Trash. *Scientific American*. <https://www.scientificamerican.com/article/world-s-oceans-clogged-by-millions-of-tons-of-plastic-trash/>
- Arkin, F. (2015). Asian states top global list of ocean plastic polluters. *SciDev.Net*.
- France-Presse A (2017) Greenpeace: PH is third worst plastic polluter of oceans. <https://newsinfo.inquirer.net/932739/greenpeace-environment-water-pollution-polluter-mani-la-bay%0ANadine>
- Ocean Crusaders (2020) Plastics Ain't So Fantastic. oceancrusaders.org/plastic-crusades/plastic-statistics/
- Reddy A V; Kolasani D (2015) Optimization of Fly Ash Content In Different Grades of Magnetic Water Concrete. *International Journal of Research in Engineering and Technology*, 4, 13, 51–56.
- De Jesus RM; Pelaez EB; Caneca M C (2018) Experimental Study on Mechanical Behaviour Of Concrete Beams With Shredded Plastics. *International Journal of GEOMATE*, 14, 42, 71–75.
- Gardner LJ; Bernal SA; Walling SA; Corkhill CL; Provis JL; Hyatt N C (2015) Characterisation of magnesium potassium phosphate cements blended with fly ash and ground granulated blast furnace slag. *Cement and Concrete Research*, 74, 78–87.
- Gregorova V; Ledererova M; Stefunkova Z (2017) Investigation of Influence of Recycled Plastics from Cable , Ethylene Vinyl Acetate and Polystyrene Waste on Lightweight Concrete Properties. *Procedia Engineering*, 195, 127–133.
- Hama SM; Hilal NN (2017) Fresh properties of self-compacting concrete with plastic waste as partial replacement of sand. *International Journal of Sustainable Built Environment*, 6, 2, 299–308.
- Hameed AM; Ahmed BA-F (2019) Employment the plastic waste to produce the light weight concrete. *Energy Procedia*, 157, 30–38. Khalil WI; Khalaf, K. J. (2017) Eco-Friendly Concrete Containing Pet Plastic Waste Aggregate. *Diyala Journal of Engineering Sciences*, 10, 1, 92–105.
- Lasco JDD; Madlangbayan MS; Sundo MB (2017) Compressive Strength and Bulk Density of Concrete Hollow Blocks (CHB) with Polypropylene (PP) Pellets as Partial Replacement for Sand. *Civil Engineering Journal*, 3, 10, 821–830.
- Manjunath BTA (2016) Partial replacement of E-plastic Waste as Coarse-aggregate in Concrete. *Procedia Environmental Sciences*, 35, 731–739.
- Nguyen H; Carvelli V; Adesanya E; Kinnunen P; Illikainen M (2018) High performance cementitious composite from alkali-activated ladle slag reinforced with polypropylene fibers. *Cement and Concrete Composites*, 90, 150–160.
- Patel HG; Dala SP (2017) An experimental investigation on Physical and Mechanical properties of Concrete with the replacement of fine aggregate by Poly Vinyl Chloride and Glass waste. 173, 1666–1671.
- Pešić N; Zivanovic S; Garcia R; Papastergiou P (2016) Mechanical properties of concrete reinforced with recycled

- HDPE plastic fibres HDPE plastic fibres . White Rose Research Online URL for this paper : Version : Accepted Version Article : Pešić, N., Živanović, S., Garcia , R. et al. Construction and Building Materials, 115, 362–270.
18. Senhadji Y; Escadeillas G; Benosman AS; Mouli M; Khelafi H; Ould Kaci S (2015) Effect of incorporating PVC waste as aggregate on the physical , mechanical , and chloride ion penetration behavior of concrete. *Journal of Adhesion Science and Technology*, 29, 7, 625–640.
 19. Babafemi AJ; Šavija B; Paul SC; Anggraini V (2018) Engineering Properties of Concrete with Waste Recycled Plastic : A Review. *Sustainability*, 10, 3875.
 20. ASTM- D1895B (2019) Intertek, 2019a.
 21. ASTM- D570 (2019) Intertek, 2019a.
 22. Neville AM (2011) *Properties of Concrete*, 5th Edn, Longman Essex (UK), ISBN: 978-0-273-75580-7 (pbk.). <http://www.pearsoned.co.uk>.
 23. Hewlett PC; Liska M (2017) *Lea’s Chemistry of Cement and Concrete*, 5th ed., Edward Arnold Ltd., London, England Google Scholar
 24. Darweesh HHM; Abo El-Suoud MR (2019) Influence of sugarcane bagasse ash substitution on Portland cement characteristics, *Indian Journal of Engineering*, 16, 252-266.
 25. Darweesh HHM; Abo El-Suoud MR (2020) Palm Ash as a Pozzolanic Material for Portland cement Pastes, *To Chemistry Journal*, 4, 72-85.
 26. Darweesh HHM (2020) Influence of Sun Flower Stalk Ash (SFSA) on the behavior of Portland cement pastes, *Results in Engineering*, 8, 100171.
 27. Darweesh HHM; Aboel-Suoud MR (2020) Effect of Agricultural Waste Material on the Properties of Portland Cement Pastes, *Journal of Research & Development in Material science*, 13, 1, 1360-1367.
 28. ASTM-C143 (2019) Concrete slump.
 29. Darweesh HHM; Abo El-Suoud MR (2018) Saw dust ash substitution for cement pastes-Part I”, *American j. of Construction and Building Materials*, 2, 1, 1-9.
 30. ASTM- C170-90 (1993) Standard Test Method for Compressive Strength of Dimension Stone”, 828-830.
 31. ASTM-C109M (2013) Standard Test Method for Compressive Strength of Hydraulic Cement Mortars (Using 2-in. Or [50-mm] Cube Specimens), *Annual Book of ASTM Standards*. ASTM International, West Conshohocken, PA.
 32. Hewlett PC; Liska M (2017) *Lea’s Chemistry of Cement and Concrete*, 5th ed., Edward Arnold Ltd., London, England Google Scholar
 33. The Constructor. (2018). Workability of concrete - types and effects on concrete strength. *The Constructor Civil Engineering Home*. <https://theconstructor.org/concrete/workability-of-concrete-types-strength/11739/>
 34. Sharma R; Bansal P P (2015) Use of Different Forms of Waste Plastic in Concrete – A Review. *Journal of Cleaner Production*. <https://doi.org/10.1016/j.jclepro.2015.08.042>
 35. Yang S; Yue X; Liu X; Tong Y (2015) Properties of self-compacting lightweight concrete containing recycled plastic particles. *Construction and Building Materials*, 84(2015), 444–453.
 36. Senhadji Y; Escadeillas G; Benosman AS; Mouli M; Khelafi H; Ould Kaci S (2015) Effect of incorporating PVC waste as aggregate on the physical, mechanical, and chloride ion penetration behavior of concrete. *Journal of Adhesion Science and Technology*, 29(7), 625–640.
 37. Kulkarni R; Oluwafisayo O (2017) *Mass Concrete - What is Mass Concrete & Where It Is Used*. *Daily Civil*. <http://www.dailycivil.com/mass-concrete>
 38. Ibrahim AA; Abdel-Megied AE; Selim MS; Darweesh HHM; Ayoub MM (2013) New Polymeric Admixture for Cement Based on Hyperbranched Poly Amide-Ester with Pentaerythritol Core, *ISRN Materials Science*, Volume 2013, Article ID 270987, 1-7.
 39. Ramli M; Tabassi AA (2012) Effects of polymermodification on the permeability of cement mortars under different curing conditions: a correlational study that includes pore distributions, water absorption and compressive strength, *Construction and Building Materials*, vol. 28, 561–570.
 40. Azhdarpour AM; Nikoudel MR; Taheri M (2016) The effect of using polyethylene terephthalate particles on physical and strength-related properties of concrete; A laboratory evaluation. *Construction and Building Materials*, 109, 55–62.